

AD-A182 965

COMPARISON OF REACTIVITY BASED ON INTERCALATION AND
HOST LATTICE RECONSTR. (U) WISCONSIN UNIV-MADISON DEPT
OF CHEMISTRY G L ROSENTHAL ET AL. 00 JUL 87

1/1


UNCLASSIFIED

UNIS/DC/TR-87/3 N00014-85-K-0631

F/G 7/2

NL



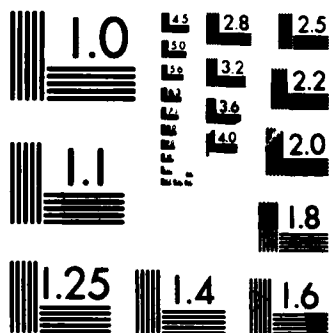

MICROCOPY RESOLUTION TEST CHART
NATIONAL BUREAU OF STANDARDS 1963-A

12

OFFICE OF NAVAL RESEARCH

Contract N00014-85-K-0631

DTIC FILE COPY

R&T Code 4134003

Technical Report No. UWIS/DC/TR-87/3

Comparison of Reactivity Based on Intercalation and Host
Lattice Reconstruction. Two Routes for the Conversion of
the Lamellar Solid Hydrogen Uranyl Phosphate to a Lamellar
Hydrate of Uranyl Phosphate

by

Guy L. Rosenthal and Arthur B. Ellis*

Prepared for Publication in the
Journal of the American Chemical Society

University of Wisconsin
Department of Chemistry
Madison, Wisconsin 53706

July 8, 1987

Reproduction in whole or in part is permitted for any
purpose of the United States Government

This document has been approved for public release and
sale; its distribution is unlimited.

*To whom all correspondence should be addressed

DTIC
ELECTE
JUL 21 1987
E

AD-A182 965


SECURITY CLASSIFICATION OF THIS PAGE

REPORT DOCUMENTATION PAGE

1a. REPORT SECURITY CLASSIFICATION NA		1b. RESTRICTIVE MARKINGS NA	
2a. SECURITY CLASSIFICATION AUTHORITY NA		3 DISTRIBUTION/AVAILABILITY OF REPORT Distribution Unlimited; Approved for Public Release	
2b. DECLASSIFICATION/DOWNGRADING SCHEDULE NA			
4. PERFORMING ORGANIZATION REPORT NUMBER(S) UWIS/DC/TR-87/3		5. MONITORING ORGANIZATION REPORT NUMBER(S) NA	
6a. NAME OF PERFORMING ORGANIZATION Chemistry Department University of Wisconsin-Madison	6b. OFFICE SYMBOL (If applicable) NA	7a. NAME OF MONITORING ORGANIZATION ONR	
6c. ADDRESS (City, State, and ZIP Code) 1101 University Avenue Madison, WI 53706		7b. ADDRESS (City, State, and ZIP Code) 800 N. Quincy Street Arlington, VA 22217	
8a. NAME OF FUNDING/SPONSORING ORGANIZATION	8b. OFFICE SYMBOL (If applicable)	9. PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER Contract N00014-85-K-0631	
8c. ADDRESS (City, State, and ZIP Code)		10. SOURCE OF FUNDING NUMBERS	
		PROGRAM ELEMENT NO	PROJECT NO
		TASK NO	R&T Code 4134003
		WORK UNIT ACCESSION NO	
11. TITLE (Include Security Classification) Comparison of Reactivity Based on Intercalation and Host Lattice Reconstruction. Two Routes for the Conversion of the Lamellar Solid Hydrogen Uranyl Phosphate to a Lamellar Hydrate of Uranyl Phosphate			
12. PERSONAL AUTHOR(S) Guy L. Rosenthal and Arthur B. Ellis			
13a. TYPE OF REPORT Technical	13b. TIME COVERED FROM TO	14. DATE OF REPORT (Year, Month, Day) 2/20/87	15. PAGE COUNT 9
16. SUPPLEMENTARY NOTATION Prepared for publication in the Journal of the American Chemical Society			
17. COSATI CODES		18. SUBJECT TERMS (Continue on reverse if necessary and identify by block number) hydrogen uranyl phosphate; uranyl phosphate; intercalation	
FIELD	GROUP		
19. ABSTRACT (Continue on reverse if necessary and identify by block number) The lamellar solid hydrogen uranyl phosphate (HUP), HUO_2PO_4 , can be quantitatively converted to a lamellar hydrate of uranyl phosphate (UP), $(\text{UO}_2)_3(\text{PO}_4)_2 \cdot 8\text{H}_2\text{O}$, by two routes: an intercalative ion-exchange reaction with aqueous UO_2^{2+} ions and thermal decomposition in an aqueous slurry. An X-ray powder pattern of the product can be indexed in tetragonal symmetry with an interlamellar spacing of 11.1 Å, expanded from a value of 8.69 Å in HUP. Conversion of HUP to UP is accompanied by a drastic diminution in photoluminescence lifetime and intensity. Arrhenius parameters derived from the rates of the intercalation and thermal decomposition reactions indicate that they proceed by quite different mechanisms: the intercalation reaction proceeds with an apparent activation energy, E_a , of 12 ± 2 kcal/mol and a $\ln A$ value of 5 ± 2 ; thermal decomposition, involving reconstruction of the host lattice, is characterized by an E_a value of 30 ± 2 kcal/mol and a $\ln A$ value of 28 ± 3 . Samples of UP, obtained by either method, can be converted back to HUP by the action of dilute phosphoric acid in an aqueous slurry at room temperature. Possible mechanisms for these reactions are discussed.			
20. DISTRIBUTION/AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED/UNLIMITED <input type="checkbox"/> SAME AS RPT <input type="checkbox"/> DTIC USERS		21. ABSTRACT SECURITY CLASSIFICATION Distribution Unlimited	
22a. NAME OF RESPONSIBLE INDIVIDUAL Arthur B. Ellis		22b. TELEPHONE (Include Area Code) 608-262-0421	22c. OFFICE SYMBOL


The solid-state structural changes accompanying intercalation can be profound and have been used to analyze interactions of guest species with host lattices.¹ We and others have studied hydrogen uranyl phosphate (HUP), HUO_2PO_4 , and demonstrated that the lamellar solid readily undergoes intercalative ion-exchange reactions, eq. 1.²⁻⁶

Typically, the protons



residing between the $(\text{UO}_2\text{PO}_4)_n^{n-}$ sheets can be exchanged simply by slurrying the HUP powder in an aqueous solution containing the ion to be intercalated.

It occurred to us that use of UO_2^{2+} as the intercalant in eq. (1) would lead to formation of uranyl phosphate (UP), $(\text{UO}_2)_3(\text{PO}_4)_2$. Furthermore, the report⁷ that UP can be prepared from an aqueous HUP slurry by thermal decomposition, eq. 2, provided us with a novel



opportunity to compare two pathways to the same product. We report herein that HUP can be quantitatively converted by intercalation (eq. 1) or host lattice reconstruction (eq. 2) to a common lamellar hydrate of UP; both reactions are reversible at room temperature. Moreover, an Arrhenius treatment of calculated rates for the forward reactions supports the notion that they proceed by quite different mechanisms.

Intercalation was typically effected by slurrying 300 mg of HUP powder⁷ in 20 mL of a 0.5 M aqueous solution of $\text{UO}_2(\text{NO}_3)_2 \cdot 6\text{H}_2\text{O}$ for several hours. Elemental analysis is consistent with a formula of $(\text{UO}_2)_3(\text{PO}_4)_2 \cdot 8\text{H}_2\text{O}$.^{8a}

Author	
Editor	<input checked="" type="checkbox"/>
Reviewer	<input type="checkbox"/>
Publication	<input type="checkbox"/>
Publication/	
Stability Codes	
Avail and/or	
Special	



A-1

A Debye-Scherrer X-ray powder diffraction pattern^{4,9} of the poorly-crystalline solid is dominated by a phase that closely matches that previously reported for $(\text{UO}_2)_3(\text{PO}_4)_2 \cdot 8\text{H}_2\text{O}$.¹⁰ Although we have been unable to obtain single crystals of the intercalated solid, its structure can be inferred from its synthesis by ion exchange and its X-ray data, which can be indexed on the basis of a tetragonal cell with $a = 6.93 \text{ \AA}$, comparable to its value in HUP, and $c = 11.1 \text{ \AA}$, expanded from an interlamellar spacing of 8.69 \AA in HUP.² These results imply that $(\text{UO}_2)_3(\text{PO}_4)_2 \cdot 8\text{H}_2\text{O}$, like the family of $\text{M}^{n+}_{1/n}\text{UO}_2\text{PO}_4 \cdot 3\text{H}_2\text{O}$ compounds,¹¹ is a structural relative of HUP with UO_2^{2+} ions occupying sites between the $(\text{UO}_2\text{PO}_4)_n^{n-}$ sheets. The unit cell expansion of 2.4 \AA corresponds to the van der Waals diameter of the uranyl oxygen atoms¹² and suggests that the principal rotation axes of the interlamellar UO_2^{2+} ions lie parallel to the sheets.

Unlike HUP, the intercalated solid exhibits only weak photoluminescence (PL) at 295 K and has a lifetime of 5-10 usec, considerably shorter than the HUP value of $\sim 450 \text{ usec}$.² The quenching may result from host-to-guest energy transfer,²⁻⁴ with the interlamellar UO_2^{2+} guest ions serving as efficient centers for nonradiative decay.

Rates for the intercalation reaction were estimated between 0 and 25°C (above which HUP begins to decompose, vide infra) by determining the time needed for characteristic HUP reflections to disappear from the powder pattern; rates (mol/sec) were independent ($\pm 10\%$) of slurry concentration (1.0-20.0 g/L) and UO_2^{2+} ion concentration (0.5-1.0 M). Figure 1 presents an Arrhenius plot of the data, yielding an apparent

activation energy (E_a) of 12 ± 2 kcal/mol and $\ln A$ value of 5 ± 2 .

Having prepared uranyl phosphate by intercalation, eq. 1, we then synthesized it by slurrying HUP in water (typically, 100 to 1000 mg in 20 mL) at elevated temperatures. Loss of PL intensity from the slurry provided a convenient means for following the reaction.¹³ The solids isolated after heating were also analyzed to be $(UO_2)_3(PO_4)_2 \cdot 8H_2O$ ^{8b} and had virtually identical IR spectra,^{8a} X-ray powder diffraction data,⁹ and PL properties to the intercalated samples. During the reaction, the pH of the system dropped from ~7 to 3.5, consistent with loss of H_3PO_4 from the lattice, eq. 2.

For kinetic analysis, we arbitrarily used the time needed to reach 25% of the initial PL intensity as a measure of reaction rate;¹⁴ typical PL decay curves are shown in the inset of fig. 1. An Arrhenius treatment of the data in fig. 1 (45–75°C) yields an apparent E_a value of 30 ± 2 kcal/mol and a $\ln A$ value of 28 ± 3 . The rate of decomposition was found to increase by ~20% when neutral pH was maintained throughout the reaction and to decrease by ~30% when the reaction was performed in 0.001 M H_3PO_4 , but the apparent E_a values were unaffected.

Samples of UP prepared by the thermal decomposition reaction revert to HUP if left in the mother liquor at room temperature for 48 hours. The HUP thus recovered was somewhat less crystalline than unreacted samples, but had equally intense PL and no UP present in the X-ray patterns. Air-dried samples of UP, obtained either by decomposition or intercalation, return to HUP at similar rates over a 3-day period when stirred in 0.01 M H_3PO_4 at 25°C.

Although intercalation and host lattice reconstruction yield the same solid, the difference in calculated Arrhenius parameters is striking and consistent with a change in mechanism. The larger E_a and $\ln A$ values found for the thermal decomposition of HUP might arise from complete dissolution and subsequent reprecipitation of the solid. Alternatively, the reaction's reversibility suggests a "self-intercalation" mechanism, in which the elevated temperature increases the solubility of HUP. The uranyl ions thus liberated are then free to exchange with protons in undissolved HUP to give the observed products. The significance of the Arrhenius parameters is being assessed by characterization of related systems in our laboratories.

Acknowledgments: The authors wish to thank Prof. Hyuk Yu, Dr. Hong Doo Kim, and Mr. Peter Dorhout for experimental assistance and Prof. S.H. Langer and a reviewer for helpful comments. We thank the Office of Naval Research for support of this research.

References


1. Intercalation Chemistry; Whittingham, M.S.; Jacobson, A.J., Eds.; Academic Press: New York, 1982.
2. Olken, M.M.; Biagioni, R.N.; Ellis, A.B. Inorg. Chem. **1983**, 22, 4128.
3. Olken, M.M.; Ellis, A.B. J. Am. Chem. Soc. **1984**, 106, 7468.
4. Olken, M.M.; Verschoor, C.M.; Ellis, A.B. Inorg. Chem. **1986**, 25, 80.
5. Pozas-Tormo, R.; Moreno-Real, L.; Martinez-Lara, M.; Bruque-Gomez, S. Can. J. Chem. **1986**, 64, 30.
6. Pozas-Tormo, R.; Moreno-Real, L.; Martinez-Lara, M.; Rodriguez-Castellon E. Can. J. Chem. **1986**, 64, 35.
7. Weigel, F.; Hoffman, G. J. Less-Common Mets. **1976**, 44, 99. Our powders were hand-ground with an agate mortar and pestle immediately before use. The mean particle size of the resulting powder was typically 2.5 μm , as determined by quasielastic light scattering, as described in: Yu, H. J. Res. NBS, **1981**, 86, 571.
8. a) Anal. (Galbraith) Calcd for $\text{H}_{16}\text{O}_{22}\text{P}_2\text{U}_3$: H, 1.40; P, 5.42; U, 62.41. Found: H, 1.40; P, 5.37; U, 61.80. IR (nujol): 1625 (m) (H_2O), 1165 (s) (PO_4^{3-}), 1060 (vs) (PO_4^{3-}), 980 (m) (PO_4^{3-}), 930 (vs) (UO_2^{2+}), 850 (m) (UO_2^{2+}). b) Anal. Calcd (see above). Found: H, 1.45; P, 5.33; U, 61.99.
9. X-ray powder diffraction reflections: $d(\text{\AA}) = 11.09(\text{s})$, $6.86(\text{m})$, $5.56(\text{m})$, $4.59(\text{s})$, $3.71(\text{m})$, $3.28(\text{s})$, $2.96(\text{s})$, $2.17(\text{w})$, $2.07(\text{w})$, $1.40(\text{m})$, $1.18(\text{ms})$ and $1.13(\text{ms})$. A weak, broad line also appears at $d = 4.21 \text{ \AA}$, indicating the presence of a small amount (<5%) of tetrahydrate in air-dried samples.

10. Pavkovic, N.; Markovic, M. *Radiochim. Acta* **1983**, *34*, 127. The reported powder pattern is more complex than ours, but can be indexed on the basis of a cell that is slightly orthorhombically distorted from the tetragonal cell described in the text.

11. Pavkovic, N.; Markovic, M.; Kojic-Prodic, B. *Croat. Chem. Acta* **1982**, *55*, 405.

12. Shannon, R.D. *Acta Crystallogr.* **1976**, *A32*, 751.

13. When the reaction is monitored by powder X-ray diffraction, it is found to proceed through an initial loss of crystallinity of HUP, accompanied by loss of PL intensity. Our results, which yield rates for the disappearance of HUP, do not permit us to say whether direct conversion of HUP to UP occurs, because the pattern of UP does not begin to appear until shortly before the PL intensity reaches a minimum; the UP pattern then grows in intensity and sharpens as the reaction proceeds. When HUP is heated above $\sim 75^{\circ}\text{C}$, reflections are observed that indicate the presence of increasing amounts of




The octahydrate, like HUP, can be completely converted to the tetrahydrate by stirring the solid in boiling water for 5 h: Pham-Thi, M.; Colombari, P. J. *Less-Common Metals*. **1985**, *108*, 189. DSC traces of the octahydrate reveal a phase change at 110°C , resulting in the tetrahydrate phase, as verified by X-ray data.

14. This corresponds to substantial structural conversion; similar E_a values are found if 50% and 10% of the initial PL intensity are used to characterize the reaction rate or if reaction rates are based on the disappearance of HUP from the powder pattern of the solid product.

Figure Caption

Arrhenius plots for the conversion of hydrogen uranyl phosphate to uranyl phosphate by thermal decomposition in water (squares) and by stirring with UO_2^{2+} ions (triangles). Decomposition experiments were conducted with 200 mg of HUP in 20 mL of triply-distilled H_2O ; for the intercalation reaction, 300 mg of HUP and a 0.5 M $\text{UO}_2(\text{NO}_3)_2$ solution were used. Each data point is the average of 2-4 runs. Slurries were stirred vigorously at temperatures maintained with an oil bath to $\pm 0.5^\circ\text{C}$. Inset: Representative PL decay curves for HUP decomposition at a) 60°C and b) 70°C . The initial PL intensities have been offset for clarity.

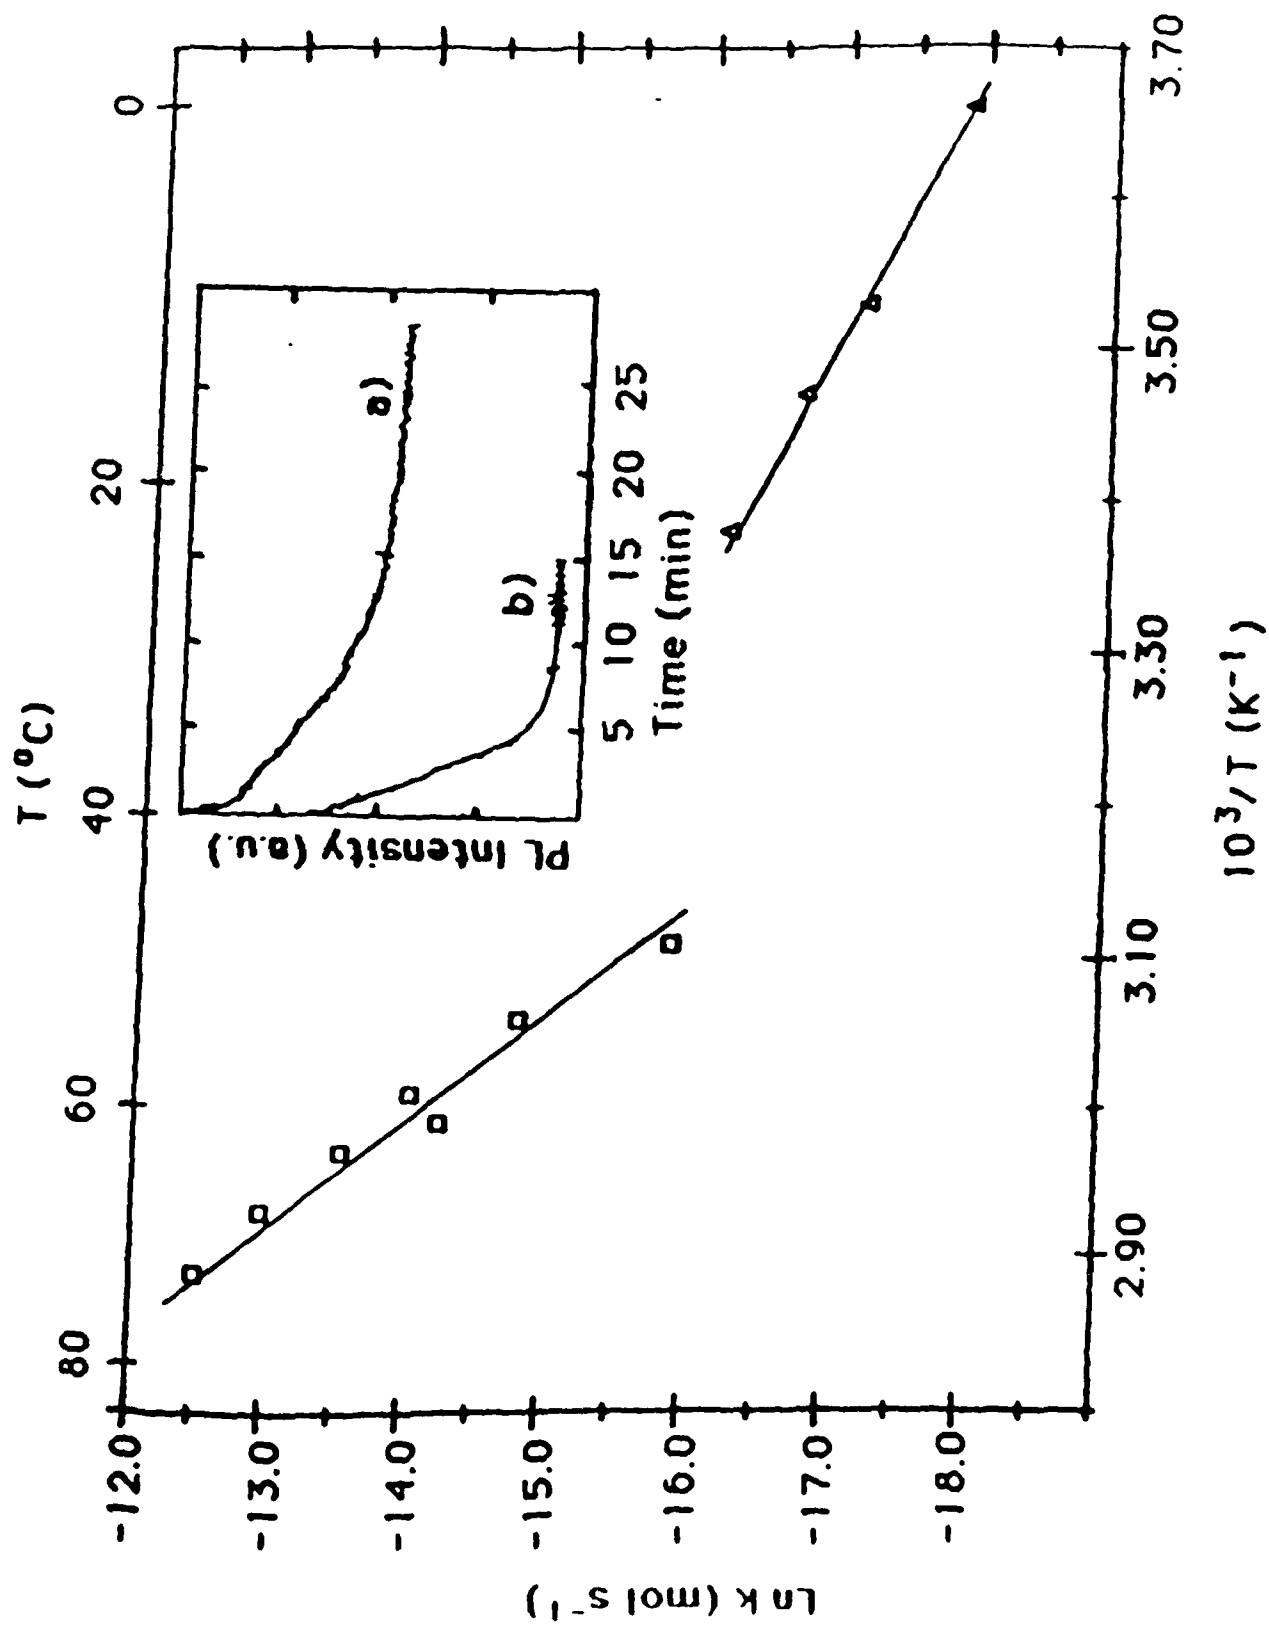

END

9-87

Dtic